

Scaling of Coulomb pseudo-potential in *s*-wave narrow-band superconductors

Tae-Ho Park and Han-Yong Choi

*Department of Physic, Institute for Basic Science Research,
and BK21 Physics Research Division,
Sung Kyun Kwan University, Suwon 440-746, Korea.*

(Dated: February 1, 2008)

Abstract

The Coulomb pseudo-potential μ^* is extracted by fitting the numerically calculated transition temperature T_c of the Eliashberg-Nambu equation which is extended to incorporate the narrow-band effects, that is, the vertex correction and the frequency dependence of the screened Coulomb interaction. It is shown that even for narrow-band superconductors, where the fermi energy ϵ_F is comparable with the phonon frequency ω_{ph} , the Coulomb pseudo-potential is a pertinent parameter, and is still given by $\mu^* = \mu/[1 + \mu \ln(\epsilon_F/\omega_{ph})]$, provided ω_{ph} is appropriately scaled.

It is generally agreed that the superconducting properties of the fulleride superconductors can be understood in terms of phonon-mediated s -wave pairing. The relevant physical parameters are: the logarithmically averaged phonon frequency $\omega_{ln} \approx 0.1$ eV, the Fermi energy $\epsilon_F \approx 0.2-0.3$ eV, the dimensionless electron-phonon coupling constant $\lambda \approx 0.7-0.8$, and the Coulomb repulsion $\mu = V_C(\omega = 0)N_F \approx 0.3-0.4$, where $V_C(\omega)$ and N_F are, respectively, the screened Coulomb repulsion and electronic density of states at the Fermi level [1, 2]. Therefore, in fullerides we have $\epsilon_F \sim \omega_{ln}$ unlike the conventional metals where $\epsilon_F \gg \omega_{ln}$. In this case, the Coulomb pseudo-potential μ^* , which is given by $\mu^* = \mu/[1 + \mu \ln(\epsilon_F/\omega_{ph})]$, is not much reduced from μ as ϵ_F becomes comparable with the average phonon frequency ω_{ph} (see below for further discussion on ω_{ph} and ω_{ln}). The observations that the value of $\ln(\epsilon_F/\omega_{ph})$ is large, typically 5–10 in conventional wide-band superconductors, and that the frequency dependence of the screened Coulomb interaction is negligible in the phonon frequency region are crucial in introducing the concept of μ^* [3]. Both of these observations do *not* hold in the fullerenes because $\epsilon_F \sim \omega_{ln}$, and, consequently, it is not clear whether the concept of Coulomb pseudo-potential is still valid in this case. In the present Letter, therefore, we study the Eliashberg equation extended to narrow-band superconductors to check if the Coulomb pseudo-potential remains a pertinent parameter as in the wide-band superconductors, that is, if T_c is determined solely by ω_{ln} , λ and μ^* , where μ^* is independent of λ and contains all the effects of the Coulomb repulsion. We first obtain the superconducting transition temperature T_c by numerically solving the Eliashberg-Nambu equation. Then, the calculated T_c values were fitted with a modified T_c form which is a function of λ and μ , in order to extract μ^* . We find that even for narrow-band superconductors the Coulomb pseudo-potential is a physically relevant concept, and is still given by $\mu^* = \mu/[1 + \mu \ln(\epsilon_F/\omega_{ph})]$, provided that ω_{ph} is appropriately scaled.

For wide-band superconductors, the frequency dependence of the screened Coulomb interaction is not important. The reason is that $V_C(\omega)$ does not change much on the phonon frequency scale of ω_{ph} when $\epsilon_F \gg \omega_{ph}$, since the frequency scale over which $V_C(\omega)$ varies is ϵ_F and the pairing kernel becomes negligible beyond the region of width ω_{ph} around the Fermi surface. This does not hold for narrow-band superconductors, and it may be important to take ω dependence of $V_C(\omega)$ into account. We do this by modeling the Coulomb repulsion in terms of the onsite Hubbard repulsion and calculating its screening self-consistently. Another complication for narrow-band superconductors is that the Migdal theorem does

not hold and the vertex correction may become important. The vertex correction is included in the present work following the Nambu method [4]. These extensions, that is, (a) frequency dependence of the screened Coulomb interaction and (b) vertex correction, are included in the Eliashberg equation. Gunnarsson and his coworkers pointed out that the procedures of screening and renormalizing away the high energy states beyond a cutoff frequency do not commute in narrow-band superconductors [5], and there arises a subtle problem in the concept of Coulomb pseudo-potential. This problem does not occur in the present approach. Including the full frequency dependence of the self-consistently screened $V_C(\omega)$ in the Eliashberg equation unnecessitates the introduction of the cutoff frequency in manipulating $V_C(\omega)$ in the Eliashberg T_c equation [6], which becomes ill-defined in the narrow-band superconductors.

It is straightforward to derive the Eliashberg-Nambu (EN) equation for finite bandwidth superconductors in the Matsubara frequency [7]:

$$\begin{aligned} W_n &= p_n + \frac{1}{\beta} \sum_m \frac{2\theta_m}{\sqrt{W_m^2 + \phi_m^2}} \{ \lambda_+ (v_1 W_m - v_2 \phi_m) - \lambda_- v_3 \phi_m \}, \\ \phi_n &= \frac{1}{\beta} \sum_m \frac{2\theta_m}{\sqrt{W_m^2 + \phi_m^2}} \{ \lambda_- (v_1 \phi_m + v_2 W_m) + \lambda_+ v_3 W_m \}, \end{aligned} \quad (1)$$

where $p_n = 2\pi T(n + 1/2)$ is the Matsubara frequency, $\theta_n = \tan^{-1} [\epsilon_F / (Z_n \sqrt{p_n^2 + \Delta_n^2})]$, and T is the temperature. $W_n \equiv p_n Z_n$ and $\phi_n \equiv \Delta_n Z_n$, where $\Delta_n \equiv \Delta(ip_n)$ and $Z_n \equiv Z(ip_n)$ are, respectively, the superconducting pairing and the renormalization functions when analytically continued into the real frequency ($ip_n \rightarrow \omega + i\delta$), and

$$\begin{aligned} \lambda_+ &= \lambda_{ph}(n - m) - \lambda_{ch}(n - m) + \lambda_{sp}(n - m), \\ \lambda_- &= \lambda_{ph}(n - m) - \lambda_{ch}(n - m) - \lambda_{sp}(n - m). \end{aligned} \quad (2)$$

Here, $\lambda_{ph}(n - m)$ is the pairing kernel due to the electron-phonon interaction at the Matsubara frequency $(p_n - p_m) = 2\pi(n - m)T$ given by

$$\lambda_{ph}(n - m) = \int_0^\infty d\Omega \frac{N_F 2\Omega \alpha^2 F(\Omega)}{\Omega^2 + (p_n - p_m)^2}, \quad (3)$$

where $\alpha^2 F(\Omega)$ is the phonon spectral function. λ_{ch} and λ_{sp} are, respectively, the interactions in the charge and spin channels due to the Hubbard repulsion U , and are determined self-consistently as

$$\begin{aligned} \lambda_{ch}(n - m) &= UN_F \{ 1/2 - (\chi_n + \chi_s) + (\chi_n + \chi_s)^2 \ln[1 + 1/(\chi_n + \chi_s)] \}, \\ \lambda_{sp}(n - m) &= UN_F \{ 1/2 + (\chi_n - \chi_s) + (\chi_n - \chi_s)^2 \ln[1 - 1/(\chi_n - \chi_s)] \}, \end{aligned} \quad (4)$$

where $\chi_n(n-m)$ and $\chi_s(n-m)$ are the dimensionless susceptibilities from, respectively, the normal and pairing processes given by [7]

$$\begin{aligned}\chi_n(k) &= \frac{N_F U}{\epsilon_F} \frac{1}{\beta} \sum_l \frac{\theta_l \theta_{k+l} p_l p_{k+l}}{\sqrt{p_l^2 + \Delta_l^2} \sqrt{p_{k+l}^2 + \Delta_{k+l}^2}}, \\ \chi_s(k) &= \frac{N_F U}{\epsilon_F} \frac{1}{\beta} \sum_l \frac{\theta_l \theta_{k+l} \Delta_l \Delta_{k+l}}{\sqrt{p_l^2 + \Delta_l^2} \sqrt{p_{k+l}^2 + \Delta_{k+l}^2}}.\end{aligned}\quad (5)$$

The finite bandwidth is explicitly incorporated through the factor θ , which is equal to $\pi/2$ in the conventional infinite bandwidth case. Finally, the vertex corrections are included by extending the Nambu method [4]. The vertex functions are given by

$$\begin{aligned}v_1 &= \frac{W_n - W_m}{p_n - p_m}, \\ v_2 &= \phi_n \frac{p_n - p_m}{(p_n - p_m)^2 + \omega_{pl}^2}, \\ v_3 &= \phi_m \frac{p_n - p_m}{(p_n - p_m)^2 + \omega_{pl}^2},\end{aligned}\quad (6)$$

where ω_{pl} is the plasma frequency which is taken to be 1 eV. Without the vertex correction, which corresponds to $v_1 = 1$ and $v_2 = v_3 = 0$, Eq. (1) is of the same form as in the theory used to study spin fluctuation effects on superconductivity [8]. Self-consistent solution of Eq. (1) together with Eqs. (2)–(6) yields $Z(ip_n)$ and $\Delta(ip_n)$ in the Matsubara frequency. Details of the formulation will be reported elsewhere [9].

It is simple to calculate T_c from the EN equation of Eq. (1). It is identified as the highest temperature at which the pairing function Δ is non-vanishing. The input parameters for solving the coupled EN equations are: $\alpha^2 F(\Omega)$ (which determines ω_{ln} and λ), U , and ϵ_F . Note that the long range part of the Coulomb interaction V_q is not included in the present study. This may be justified for the case where the average of V_q is small compared with the onsite Hubbard repulsion U : $\langle V_q \rangle_{ave} / U \approx 4\pi n e^2 / k_F^2 U \ll 1$. Alternatively, U may be considered as a partially screened value due to the metallic screening of the long range part of the Coulomb interaction. The ω_{ln} is given by

$$\omega_{ln} = \exp \left[\frac{2}{\lambda} \int_0^\infty d\Omega \ln \Omega \frac{1}{\Omega} N_F \alpha^2 F(\Omega) \right], \quad (7)$$

where $\lambda = N_F V$, $\mu = U N_F$, and $V = 2 \int_0^\infty d\Omega \alpha^2 F(\Omega) / \Omega$. We take $\alpha^2 F(\Omega)$ as a sum of three truncated Lorentzians appropriate for fullerene superconductors [7]. This choice of $\alpha^2 F(\Omega)$ gives the logarithmically averaged phonon frequency $\omega_{ln} = 0.094$ eV. μ is varied between 0

and 0.4 and λ between 0.4 and 1.2 to calculate T_c , from which to extract an extended T_c formula and the Coulomb pseudo-potential μ^* .

The EN equation was solved by iterations, for various values of λ and μ to find T_c . Self-consistency is achieved with a few tens of iterations except when T is close to T_c . These results are used to extract a modified T_c formula following the same procedure as McMillan and Allen (MA) [10]. The MA T_c equation is given by

$$T_c = \frac{\omega_{ln}}{1.2} \exp \left[-\frac{1.04(1 + \lambda)}{\lambda - \mu^*(1 + 0.62\lambda)} \right], \quad (8)$$

which was extracted by fitting to numerical T_c calculations of the Eliashberg equation. The McMillan-like procedure for extracting T_c formula proceeds as follows [10]: Firstly, for the case of zero Coulomb potential, $\mu = \mu^* = 0$, we estimate the λ dependence of T_c by taking

$$\ln \left[\frac{\omega_{ln}}{T_c} \right] = a + \frac{b}{\lambda} + \frac{c}{\lambda^2}, \quad (9)$$

where a , b , and c are the constants to be determined by fitting to the exact numerical results obtained by solving EN equation of Eq. (1). The MA case corresponds to $a, b \neq 0$ and $c = 0$. Non-zero c introduces higher power of $1/\lambda$ in the T_c formula due to the narrow bandwidth effects considered here, that is, the vertex correction and frequency dependence of the effective Coulomb interaction. McMillan used an approximate solution of the Eliashberg equation to guide the choice of the functional form of Eq. (9). From a solution of a version of a square-well potential model, the form of $\ln(\omega_{ln}/T_c) = a + b/\lambda$ was anticipated [10]. The simplest correction coming from beyond the simple model will be of the form $1/\lambda^2$ as incorporated in Eq. (9). For the parameter values appropriate for the fulleride superconductors, we obtain $a = 1.13$, $b = 0.765$, and $c = 0.033$. This should be compared with the MA case, $a = 1.22$, $b = 1.04$, and $c = 0$. The obtained values for a , b , and c depend weakly on the particular choice of ϵ_F/ω_{ln} and $\alpha^2 F$.

Secondly, to include the effects of non-zero Coulomb interaction on T_c ($\mu \neq 0$), we take the form

$$\ln \left[\frac{\omega_{ln}}{T_c} \right] = \frac{a\lambda^2 + b\lambda + c}{\lambda^2 - \mu^{**}(\mu, \lambda)}. \quad (10)$$

as with MA. Here, a , b , and c have already been determined from the first fitting process, and μ^{**} depends on μ and λ . For the MA case, $\mu^{**} = \mu^*(1 + 0.62\lambda)$, where

$$\mu^* = \mu / [1 + \mu \ln(\epsilon_F/\omega_{ph})] \quad (11)$$

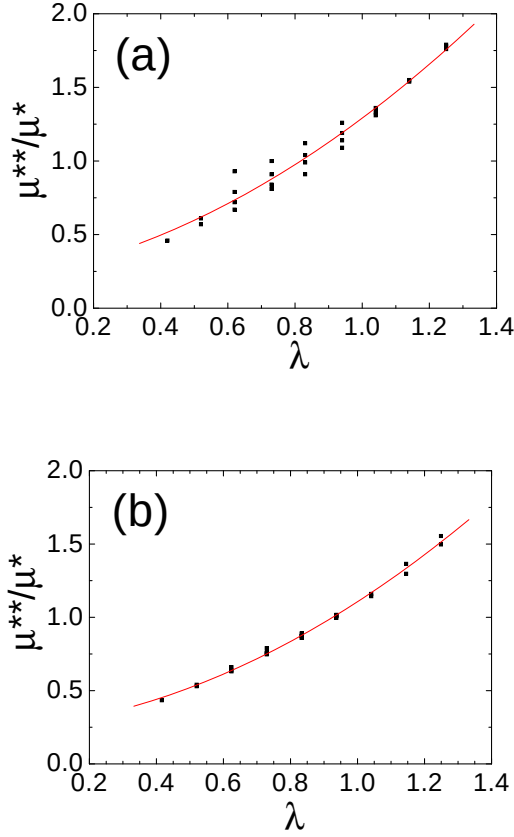


FIG. 1: Determining $S = \omega_{ph}/\omega_{ln}$ by requiring μ^{**}/μ^* be independent of μ , when the bandwidth B is 0.5 eV. λ is varied from 0.4 to 1.2, and, for each λ , four μ values, 0.1, 0.2, 0.3, and 0.4, were taken to calculate μ^{**}/μ^* . (a) When $S = 1$. It is clear that for each λ , the four calculated points corresponding to four different μ values are scattered in the plot. (b) When $S = 2$, the scattered 4 points in the figure (a) scale to collapse on to a single point for each λ .

as given by Morel and Anderson [11]. We put

$$\mu^{**} \equiv \mu^* f(\lambda), \quad (12)$$

where $f(\lambda)$ is a function of λ to be determined by fitting, and μ^* is assumed, in the present case as well, to take the same Coulomb pseudo-potential form of Eq. (11). Then, $f(\lambda)$ can be written as

$$f(\lambda) = \frac{1 + \mu \ln(\epsilon_F/\omega_{ph})}{\mu} \left[\lambda^2 - \frac{(a\lambda^2 + b\lambda + c)}{\ln(\omega_{ln}/T_c)} \right]. \quad (13)$$

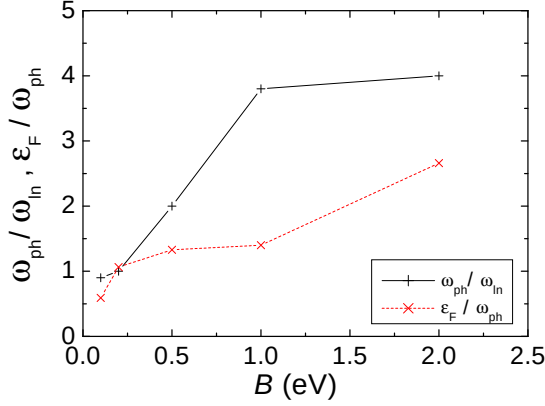


FIG. 2: $S = \omega_{ph}/\omega_{ln}$ as a function of the bandwidth B . S was determined by requiring μ^{**}/μ^* be independent of μ for a given bandwidth. The + and $\times$ are, respectively, calculated values for S and ϵ_F/ω_{ph} . The solid and dashed lines are a guide to eyes.

We then write

$$\omega_{ph} = S\omega_{ln}, \quad (14)$$

where S is to be determined by requiring that $\mu^{**}/\mu^* = f(\lambda)$ be *independent of* μ . We calculate, for a fixed λ , μ^{**}/μ^* for several values of μ . μ^{**}/μ^* , in general, will depend on μ and be scattered in the plot as shown in Fig. 1(a) for $S = 1$. For an appropriate value of S , however, the data will scale to collapse on to a single point for each λ . This is found to occur at $S = 2$ when $\epsilon_F = 0.25$ eV as can be seen in Fig. 1(b). Fitting the curve of Fig. 1(b) yields $f(\lambda) = \mu^{**}/\mu^* = 0.618\lambda^2 + 0.244\lambda + 0.244$.

This scaling behavior gives reliability to our procedures. Consequently, T_c can be written as

$$T_c = \omega_{ln} \exp \left[-\frac{a\lambda^2 + b\lambda + c}{\lambda^2 - (a'\lambda^2 + b'\lambda + c')\mu^*} \right] \quad (15)$$

MA case corresponds to $c = c' = 0$. The concept of Coulomb pseudo-potential is found to be valid and important even for a narrow-band superconductor of $\epsilon_F/\omega_{ph} \sim 1$ where retardation effects are much weaker compared with the conventional wide-band superconductors. We should note here that although we determined $S = \omega_{ph}/\omega_{ln}$ by requiring μ^{**}/μ^* be independent of μ , ω_{ph} should *not* be considered an additional fitting parameter. S remains the same for a given bandwidth irrespective of λ and μ , and gives the appropriate Coulomb pseudo-potential value μ^* for given μ and bandwidth.

We then vary the bandwidth $B = 2\epsilon_F$ to find how S varies accordingly. For each B , we repeated the fitting procedures described above to determine $S = \omega_{ph}/\omega_{ln}$ which gives the best scaling behavior. S as a function of B determined this way is shown in Fig. 2. S increases as the bandwidth is increased, and then saturates around the value of 4 when B is larger than 1 eV for $\omega_{ln} = 0.094$ eV. Note that in the Eliashberg theory, the Coulomb pseudo-potential μ^* of Eq. (11) is often rescaled with a cutoff frequency $\omega_c \approx 5 - 10 \omega_D$, where ω_D is the Debye frequency. ω_c corresponds to ω_{ph} in the present work. The value of $S \approx 4$ for $B > 1$ is consistent with the $\omega_c/\omega_D \approx 5$ often adapted for conventional wide-band superconductors [3]. Increase of S as B is increased does not mean the less effective retardation, because the increase of S is slower than that of ϵ_F . This is shown with the crosses in the plot. ϵ_F/ω_{ph} increases as B is increased, and the retardation, which is determined by ϵ_F/ω_{ph} as given by Eq. (11), is more effective for wide-band superconductors.

To summarize, we investigated whether the Coulomb pseudo-potential μ^* is still a pertinent concept in the narrow-band superconductors. Because the narrow bandwidth implies a negligible retardation effects ($\mu^* \approx \mu$), it is not clear whether the μ^* remains a relevant and useful parameter for the narrow-band superconductors like the fullerenes. To answer this question, we solved the extended Eliashberg equation which incorporates the finite bandwidth effects, namely, the frequency dependence of the effective interaction between electrons and the vertex corrections, and obtained the transition temperature T_c as the dimensionless electron-phonon coupling constant λ and the Coulomb repulsion μ are varied. The obtained numerical results were used to find a T_c formula which is valid for narrow-band superconductors and to extract the Coulomb pseudo-potential μ^* . It was found that T_c is given by the form of Eq. (15) where μ^* contains all the effects of the Coulomb repulsion and is independent of λ . Therefore, the concept of Coulomb pseudo-potential continues to be valid even for narrow-band superconductors. Another interesting and important outcome of the present study is that the Coulomb pseudo-potential is still given by $\mu^* = \mu/[1 + \mu \ln(\epsilon_F/\omega_{ph})]$ as in the conventional wide-band superconductors, provided $\omega_{ph} = S\omega_{ln}$ is appropriately scaled. Scaling of ω_{ph} and μ^* as ϵ_F is varied is also computed. Because we included the vertex correction and frequency dependent Coulomb interaction in the present work, there is no *a priori* reason that the Coulomb pseudo-potential take the same form. We established that the Coulomb pseudo-potential continues to be a pertinent parameter and is still given by the Morel-Anderson form in the narrow-band superconductors.

We would like to thank Yunkyu Bang for helpful conversations. This work was supported by Korea Science & Engineering Foundation (KOSEF) through Grant No. 1999-2-114-005-5, by Korea Research Foundation (KRF) through Grant No. KRF-2000-DP0139, and by the Ministry of Education through the Brain Korea 21 SNU-SKKU Physics Program.

- [1] A. F. Hebard, Phys. Today **45** (11), 26 (1992).
- [2] O. Gunnarsson, Rev. Mod. Phys. **69**, 575 (1997); C. H. Pennington and V. A. Stenger, Rev. Mod. Phys. **68**, 855 (1986).
- [3] P. B. Allen and B. Mitrovic, *Solid State Physics* (Academic Press, New York, 1982), vol. 37, p. 1.
- [4] Y. Nambu, Phys. Rev. **117**, 648 (1960).
- [5] O. Gunnarsson and G. Zwicknagl, Phys. Rev. Lett. **69**, 957 (1992); E. Koch, O. Gunnarsson, and R. M. Martin, Phys. Rev. Lett. **83**, 620 (1999).
- [6] J. R. Schrieffer, *Theory of Superconductivity* (Benjamin, New York, 1964).
- [7] H. Y. Choi, Phys. Rev. Lett. **81**, 441 (1998).
- [8] N. F. Berk and J. R. Schrieffer, Phys. Rev. Lett. **17**, 433 (1966).
- [9] H. Y. Choi, in preparation.
- [10] W. L. McMillan, Phys. Rev. **167**, 331 (1968); P. B. Allen and R. C. Dynes, Phys. Rev. B **12**, 905 (1975).
- [11] P. Morel and P. W. Anderson, Phys. Rev. **125**, 1263 (1962).